

Tatyana Chernozhuk and Oleg Kalugin

CONDUCTIVITY AND INTERPARTICLE INTERACTIONS IN THE SOLUTIONS OF 1-1 ELECTROLYTES IN PROPYLENE CARBONATE IN THE WIDE RANGE OF TEMPERATURES

V. N. Karazin Kharkov National University
4 Svobody Sq., 61022 Kharkov, Ukraine
tanya.chernozhuk@gmail.com

Received: November 10, 2014 / Revised: December 15, 2014 / Accepted: May 27, 2015

© Chernozhuk T., Kalugin O., 2016

Abstract. Results of conductometric investigations of solutions of several 1-1 electrolytes in propylene carbonate in the range of temperatures from 298 to 398 K are presented. Using the expanded Lee-Wheaton equation of electric conductivity, constants of ionic association are defined. It is determined that LiClO₄ in propylene carbonate is a non-associated electrolyte. In order to account on the dynamics of ionic solvation, separation into ionic components is made.

Keywords: propylene carbonate, conductivity, association, 1-1 electrolytes.

1. Introduction

Studies of the ion-molecular and ion-ionic interactions, as well as the dynamics of ions in non-aqueous solvents, are of particular interest, primarily for the development of chemical current sources (CCSs) [1, 2]. Propylene carbonate (PC) belongs to the class of ethers widely used as co-solvents for electrolytes in CCSs. This solvent is of particular interest because of its high dielectric permeability ($\epsilon^{298} = 64.92$) [3] and molecular dipole moment of the solvent ($m = 4.94$) [4], as well as the wide range of liquid state (from 224.35 to 515 K) [3] and high solubility of lithium salts in it.

In the literature there are quite many works primarily on the concentration-dependent investigations of salts solutions in PC at 298 K (Table 1), but only a few conductometric studies in diluted solutions [3, 5, 6] are known.

In almost all the works, association constants (K_A) of electrolytes in PC at 298.15 K are studied (Table 1), but

little attention is given to the limiting molar ionic conductivity (λ_0^i), from which it is possible to obtain information on the dynamics of ionic solvation. Separation into ionic components in the works [3, 7] is made with an assumption that $\lambda_0((i\text{-Am})_4\text{N}^+) = \lambda_0((i\text{-Am})_4\text{B}^-) = \Lambda_0((i\text{-Am})_4\text{N}(i\text{-Am})_4\text{B})/2$. In the works [8, 9, 10], when separating into ionic components, it was assumed that the temperature number of K⁺ in KClO₄ solutions in PC was determined accurately by R. Zana *et al.* [24]. In the work [6] separation into ionic components is made taking into account the assumption made by B. Krungalts [25] and discussed earlier, that $\lambda_0\eta_0(\text{Bu}_4\text{N}^+) = 0.2131 \text{ S}\cdot\text{cm}^2\cdot\text{P}\cdot\text{mol}^{-1}$ remains constant in various organic solvents and at various temperatures.

Proceeding from it, the purpose of the present work was to investigate influence of the temperature, size and nature of the ion on the quantitative characteristics of interparticle interactions, electrical conductivity of ions and ionic association in solutions of 1-1 electrolytes in propylene carbonate in the range of temperatures from 298.15 K to 398.15 K.

2. Experimental

PC after dehydration over anhydrous CaO within several days was subjected to fractional vacuum distillation, collecting the middle fraction. Purity was controlled by specific electrical conductivity, $k_{298.15} = 3.2\cdot 10^{-8} \text{ Sm}\cdot\text{cm}^{-2}$, and moisture presence – by Fisher method of coulometric titration (water content did not exceed 0.003 %). Physical and chemical properties of the solvent at various temperatures were found from the following polynomials described in the work [26]:

$$1/d = 0.81527 + 0.7149 \cdot 10^{-3} \cdot t + 0.459 \cdot 10^{-6} \cdot t^2 \quad (1)$$

$$h = \exp(5.3665 - 4.344 \cdot 10^3 \cdot T^{-1} + 0.87 \cdot 10^6 \cdot T^{-2}) \quad (2)$$

$$e = -33.09 + 36.65 \cdot 10^3 \cdot T^{-1} - 2.21 \cdot 10^6 \cdot T^{-2} \quad (3)$$

where d (g·cm⁻³), h (mPa·s), t (°C), T (K).

Physical and chemical properties of pure propylene carbonate at temperatures from 278.15 to 398.15 K are given in Table 2.

For the measurement of electrical conductivity of solutions, conductometric cells (5 pieces) from molybdenic glass with platinized platinum electrodes were used. The cells were calibrated in the aqueous solutions of potassium chloride [27] and their constants vary from 0.1 to 0.25 cm⁻¹.

Resistance of the solutions was measured with the bridge of alternating current P-5083 and conductometer LCR-821 at the frequency of 1 kHz.

Table 1

Data on the diluted solutions ($1 \cdot 10^{-4}$ – $1 \cdot 10^{-2}$ mol/dm³) of 1-1 electrolytes in propylene carbonate and its mixtures that have been reported in the literature

Solvents	Electrolytes	T , K	Concentration range	Defined parameters	[Ref.]
PC	(Li, Na, K, Rb, Cs, Me ₄ N, Et ₄ N, Pr ₄ N, Bu ₄ N)ClO ₄ , NaI, KI, KSCN, Bu ₄ NI, Bu ₄ NBr	298		$\Lambda_0, K_A, \Lambda_0^{\text{ion}}$	[3]
PC	(Me ₄ N, Et ₄ N)PF ₆ , Me ₄ NBF ₄ , (C ₇ H ₁₅) ₄ NPic, PyrPic, KPF ₆	298	$(4-16) \cdot 10^{-4}$ mol/dm ³	$\lambda_0^i, \lambda_0 \eta_0$	[4]
PC	CF ₃ COOLi, CHF ₂ COOLi	238–308	$(7.3-48) \cdot 10^{-4}$ mol/dm ³	Λ, K_A	[5]
PC	(Na, K, Rb, Cs, Me ₄ N, Et ₄ N, Pr ₄ N, Bu ₄ N)I, (Et ₄ N, Ph ₄ P)Br, Ph ₄ PCl, NaBPh ₄ , Bu ₄ NBPh ₄	233–318		$\Lambda_0, K_A, \Lambda_0^{\text{ion}}$	[6]
PC	LiCl, LiClO ₄	298	$1 \cdot 10^{-4}$ – $1 \cdot 10^{-2}$ mol/dm ³	$\Lambda, \Lambda_0, \lambda_0^+, \lambda_0^-$	[7]
PC	LiClO ₄	298	$9.5 \cdot 10^{-4}$ –0.4 M	$\Lambda, t^{\text{r}}(\text{Li})$	[8]
PC, AN, γ -BL	LiClO ₄ , LiAsF ₆	298	0.001–0.01 mol/dm ³	Λ, K_A	[9]
PC	(Me ₄ N, Et ₄ N, Pr ₄ N, Bu ₄ N, Am ₄ N, K)Pic	298	$(12.5-6) \cdot 10^{-4}$ mol/dm ³	$\Lambda_0, K_A, \lambda_0^i, \lambda_0 \eta$	[10]
PC+1,2-DMM	LiClO ₄ , LiAsF ₆ , <i>n</i> -Bu ₄ NClO ₄ , <i>n</i> -Bu ₄ NBPh ₄	298	$1 \cdot 10^{-2}$ – $1 \cdot 10^{-4}$ mol/dm ³	$\Lambda, \lambda_0^+, \lambda_0^-, \Lambda_0, K_A, K_A^{\text{Bjenum}}$	[11]
PC, γ -BL, PC+1,2-DME, γ -BL+1,2-DME	LiAsF ₆ , LiClO ₄ , Bu ₄ NClO ₄ , Bu ₄ NCl, Bu ₄ NBPh ₄	298	$1 \cdot 10^{-3}$ – $2 \cdot 10^{-2}$ mol/dm ³	$\Lambda, \lambda_0^{+\text{mix}}, \lambda_0^{-\text{mix}}, \Lambda_0^{\text{mix}}, \lambda_0 \eta^{\text{mix}}, K_A$	[12]
PC, γ -BL, 1,2-DME, etc.	LiX (X=ClO ₄ , AsF ₆ , BF ₄ , Cl, Br, I, NO ₃ , Pic, BPh ₄ , SCN)	298		K_A	[13]
PC+ 1,2-DME (1:1)	LiX (X=BF ₄ , CF ₃ SO ₃ , ClO ₄ , (CF ₃ SO ₃) ₂ N, AsF ₆ , PF ₆ , SO ₂ (CF ₂) ₄ SO ₂ N)	298 248–548		$\Lambda_0, \Lambda_0 \eta, \eta, \kappa$	[14]
PC	LiPF ₆ , LiBF ₄ , LiPF ₆ ·2DG, LiPF ₆ ·PMDETA	298	$1 \cdot 10^{-3}$ –1 M	$\kappa, \Lambda, \Lambda_0, \Lambda_0 \eta, \lambda_0^+, K_A$	[15]
PC	(Li, Na, K, Rb, Cs) ClO ₄	298	$1 \cdot 10^{-3}$ – $2 \cdot 10^{-2}$ mol/dm ³	Λ_0, K_A, R	[16]
PC	LiClO ₄ , etc.	228–298	1 M	Λ	[17]
PC, etc.	LiClO ₄ , LiSCN, Bu ₄ NSCN, Bu ₃ NHSCN	298	$(1.4-19) \cdot 10^{-3}$ mol/dm ³	$\Lambda_0, K_A, \Lambda_0(\text{calc})$	[18]
PC, etc.	LiC ₂ F ₅ CO ₂ , LiCF ₃ CO ₂	298	$(0.4-4) \cdot 10^{-3}$ mol/dm ³	$\Lambda_0, K_A, \Lambda_0^{\text{ion}}$	[19]
PC	Pr ₄ NBr, Bu ₄ NBr, Bu ₄ NI	223–398		Λ, η	[20]
PC etc.	Li(PF ₆ , BF ₄ , CF ₃ SO ₃ , (CF ₃ SO ₃) ₂ N, C ₄ F ₉ SO ₃)	298		λ_0^i	[21]
PC		298		Λ_0, K_A	[22]
PC, etc.	(Li, Na, K, Me ₄ N, Et ₄ N, Pr ₄ N, Bu ₄ N) ClO ₄ ; Bu ₄ N (Cl, Br, I); Li (Cl, Br, I)	298		Λ_0, K_A	[23]

Table 2

Physical properties of the pure PC at temperatures from 278 to 398 K (calculated from Eqs. 1-3, 20)

T, K	$d, g \cdot cm^{-3}$	$h, mPa \cdot s$	e	$t_D \cdot 10^{11}, s$
278.15	1.2212	4.013	70.11	5.0386
298.15	1.1999	2.592	64.97	4.1526
308.15	1.1893	2.200	62.57	3.6816
318.15	1.1787	1.922	64.97	3.2888
328.15	1.1683	1.722	58.07	2.9906
338.15	1.1578	1.575	55.97	2.6774
358.15	1.1372	1.387	52.01	2.2303
378.15	1.1168	1.289	48.37	1.8941
398.15	1.0967	1.247	45.02	1.6353

For the measurement of resistance of the solutions at the temperatures from 278.15 to 328.15 K, water thermostats were used, and for temperatures from 338.15 to 398.15 K – the oil ones. Accuracy of thermostabilization was 0.02 %.

Solutions of the electrolytes were prepared using the gravimetric method. Salts samples were weighted on the microanalytical scales GR-202 with the accuracy of $2 \cdot 10^{-5}$ g (the mass of the samples ranged within $0.2 \leq m_c \leq 1.0$ g).

Masses of the solutions were defined (according to the preliminary approximate calculation) by weighing on the scales VLA-200 or analytical scales GR-202 with the accuracy of $2 \cdot 10^{-4}$ g.

Concentration of the initial solutions expressed in moles of dissolved substance per 1 kg of solution ($n\%$) was defined by Eq. (4):

$$n\% = \frac{m_c \cdot 1000}{M_c \cdot m_p} \quad (4)$$

where m_c (g) and M_c (g/mol) – mass and molar mass of the salt, m_p (g) – mass of initial solution.

Concentrations of the solutions in the series were defined by the ratio:

$$n\%_i = \frac{n\% \cdot m_1}{m_i} \quad (5)$$

where $n\%$ and m_i – concentration and mass of the prepared solution; m_1 – sample of the initial solution.

Molar concentration of electrolytes in the solution (c) was defined as:

$$c_i(t) = n\% \cdot d_i(t) \quad (6)$$

where $d_i(t)$ – density of i solution at a particular temperature.

To prevent moisture ingress, solutions were stored in the flasks with double covers with additional sealing with the Parafilm "M" tape at the joints of the internal section.

Experimental values of the molar electric conductivity of 1-1 electrolytes in PC in a wide range of temperatures are given in Tables 3–5.

Table 3

Molar conductivities $L/S \cdot cm^2 \cdot mol^{-1}$ of 1-1 electrolytes in PC at temperatures 298.15–398.15 K

$n\% \cdot 10^4, mol \cdot kg^{-1}$	298.15 K	308.15 K	318.15 K	338.15 K	358.15 K	378.15 K	398.15 K
1	2	3	4	5	6	7	8
LiClO ₄							
3.373	26.18 ₇	29.55 ₃	33.03 ₃	40.34 ₄	48.92 ₇	57.63 ₆	67.04 ₈
4.912	26.10 ₇	29.53 ₄	32.98 ₃	40.29 ₄	48.70 ₅	57.54 ₉	66.90 ₅
6.426	26.091	29.465	32.883	40.263	48.692	57.407	66.886
8.281	26.023	29.402	32.787	40.214	48.578	57.296	66.789
10.712	–	29.292	–	40.048	–	–	66.733
13.166	25.976	29.245	32.653	39.990	48.333	56.993	66.496
15.913	25.929	29.181	32.505	39.890	48.277	56.828	66.177
18.865	25.825	29.077	32.460	39.833	48.052	56.592	65.731
22.343	25.788	28.842	32.396	39.770	47.985	56.411	65.667
25.603	25.755	28.970	32.344	39.675	47.847	56.298	65.567
29.444	25.714	28.939	32.302	39.587	47.703	56.144	65.268
31.209	25.755	28.902	32.260	39.572	47.672	56.127	65.266

Table 3 (Continued)

1	2	3	4	5	6	7	8
34.644	25.649	28.824	32.190	39.472	47.543	55.977	65.060
49.831	25.448	28.552	31.908	39.090	47.111	55.444	64.373
69.942	25.250	28.348	31.617	38.612	46.522	54.650	63.429
95.029	25.096	28.141	31.392	38.373	46.116	54.152	62.770
NaClO ₄							
7.038	27.88 ₅	–	–	51.59 ₉	65.17 ₈	–	95.04 ₇
10.026	27.72 ₂	33.40 ₃	38.87 ₅	51.33 ₂	64.92 ₆	79.58 ₆	94.95 ₈
13.164	27.66 ₄	33.00 ₃	38.65 ₇	51.05 ₅	64.68 ₁	78.93 ₉	94.65 ₄
16.200	27.60 ₂	32.90 ₅	38.55 ₁	50.89 ₇	64.46 ₄	78.71 ₃	94.07 ₆
20.689	27.53 ₂	32.85 ₄	38.49 ₇	50.82 ₁	64.38 ₇	78.67 ₅	93.83 ₆
25.431	27.51 ₀	32.81 ₂	38.46 ₂	50.81 ₁	64.30 ₆	78.46 ₈	93.77 ₉
30.405	27.49 ₁	32.79 ₂	38.42 ₃	50.71 ₂	64.27 ₅	78.32 ₉	93.62 ₅
36.619	27.39 ₅	32.65 ₁	38.27 ₂	50.66 ₇	64.11 ₉	78.15 ₄	93.34 ₈
42.286	27.35 ₁	32.58 ₇	38.18 ₈	50.55 ₂	63.99 ₃	78.15 ₅	93.22 ₆
48.141	27.28 ₉	32.53 ₅	38.13 ₂	50.50 ₁	63.84 ₅	78.16 ₉	93.01 ₂
55.744	27.24 ₉	32.50 ₇	38.09 ₁	50.36 ₆	63.65 ₁	77.78 ₃	92.96 ₉
61.212	27.22 ₂	32.46 ₁	38.04 ₄	50.55 ₁	63.68 ₆	77.64 ₀	92.00 ₂
72.295	27.18 ₁	32.19 ₅	37.88 ₂	50.38 ₅	62.94 ₀	77.44 ₉	91.80 ₅
Bu ₄ NClO ₄							
2.568	26.93 ₃	31.98 ₀	37.34 ₉	48.73 ₄	61.57 ₈	74.96 ₅	89.12 ₇
2.953	26.83 ₅	31.86 ₁	37.23 ₂	48.66 ₈	61.49 ₈	74.87 ₈	89.06 ₀
3.481	26.75 ₂	31.79 ₅	37.15 ₁	48.62 ₇	61.33 ₁	74.54 ₂	88.87 ₀
4.096	26.74 ₂	31.75 ₄	37.10 ₄	48.52 ₆	61.17 ₉	74.44 ₀	88.72 ₉
4.640	26.71 ₆	31.67 ₃	37.07 ₈	48.47 ₅	61.16 ₃	74.38 ₈	88.62 ₆
5.260	26.62 ₈	31.63 ₇	36.99 ₅	48.38 ₄	60.95 ₀	74.24 ₉	88.50 ₄
5.932	26.58 ₁	31.58 ₈	36.91 ₄	48.32 ₀	60.87 ₁	74.17 ₉	88.40 ₁
6.669	26.54 ₀	31.51 ₆	36.80 ₀	48.29 ₇	60.73 ₉	74.06 ₉	88.33 ₃
7.305	26.50 ₅	31.45 ₇	36.75 ₆	48.20 ₇	60.66 ₉	73.90 ₆	88.28 ₆
7.478	26.49 ₁	31.41 ₆	36.73 ₇	48.15 ₆	60.62 ₃	73.82 ₅	88.12 ₅
8.369	26.46 ₈	31.35 ₁	36.68 ₄	48.03 ₉	60.54 ₄	73.77 ₉	87.71 ₆
11.375	26.33 ₂	31.30 ₇	36.58 ₆	47.89 ₆	60.46 ₇	73.72 ₀	87.50 ₁
15.314	26.20 ₁	31.14 ₆	36.38 ₄	47.60 ₈	60.23 ₆	73.23 ₉	87.14 ₁
19.310	26.02 ₁	30.95 ₄	36.16 ₇	47.30 ₃	59.73 ₆	72.79 ₉	86.62 ₈
23.862	25.89 ₁	30.67 ₄	35.97 ₄	47.06 ₉	59.42 ₁	72.35 ₃	85.94 ₉
29.073	25.72 ₈	30.56 ₁	35.72 ₆	46.70 ₇	58.97 ₄	71.75 ₂	85.29 ₃
34.983	25.64 ₉	30.51 ₅	35.63 ₉	46.52 ₈	58.67 ₂	71.27 ₂	84.76 ₅
41.342	25.41 ₉	30.24 ₈	35.31 ₇	46.00 ₉	58.21 ₀	70.80 ₉	84.14 ₇
47.509	25.34 ₈	30.16 ₈	35.21 ₁	46.97 ₂	57.99 ₄	70.66 ₂	83.88 ₈
55.495	25.28 ₂	30.08 ₆	35.06 ₆	46.72 ₈	57.71 ₃	69.84 ₈	83.00 ₇
63.049	25.07 ₂	29.86 ₉	34.79 ₂	45.43 ₇	57.31 ₇	69.65 ₇	82.73 ₇
70.634	24.89 ₄	29.63 ₉	34.56 ₂	*44.54 ₇	56.90 ₉	69.11 ₉	82.40 ₁
79.710	24.79 ₂	29.43 ₉	34.42 ₄	44.48 ₂	56.65 ₀	68.91 ₈	81.79 ₈
Bu ₄ NBPh ₄							
1.250	15.78 ₅	19.24 ₆	22.87 ₆	30.91 ₀	39.66 ₄	49.01 ₈	59.18 ₉
1.939	15.71 ₅	19.14 ₄	22.79 ₀	30.88 ₀	39.51 ₇	49.01 ₂	59.10 ₃
2.178	15.64 ₁	19.07 ₆	22.71 ₁	30.81 ₉	39.50 ₁	48.77 ₈	59.00 ₅
4.228	15.50 ₃	18.84 ₃	22.47 ₉	30.42 ₀	39.34 ₈	48.52 ₈	58.64 ₆
4.422	15.44 ₅	18.85 ₁	22.39 ₉	30.36 ₂	39.13 ₉	48.29 ₃	58.62 ₂
4.781	15.35 ₆	18.69 ₉	22.26 ₈	30.17 ₁	39.06 ₇	48.10 ₈	58.40 ₀
5.592	15.35 ₃	18.66 ₁	22.25 ₈	30.11 ₇	38.88 ₆	47.99 ₇	58.35 ₈
6.475	15.26 ₄	18.60 ₈	22.14 ₉	29.99 ₃	38.85 ₃	47.98 ₅	57.83 ₃
13.539	14.96 ₇	18.14 ₇	21.55 ₉	29.26 ₇	38.65 ₈	46.73 ₂	56.61 ₄
22.025	14.62 ₈	17.73 ₂	21.07 ₈	28.64 ₄	36.82 ₀	45.85 ₅	55.37 ₇
27.884	14.51 ₂	17.58 ₈	20.90 ₃	28.43 ₄	36.55 ₈	45.36 ₈	54.79 ₂

Table 3 (Continued)

1	2	3	4	5	6	7	8
33.111	14.39 ₄	17.34 ₈	20.74 ₃	28.18 ₁	36.29 ₂	45.13 ₄	54.63 ₈
41.552	14.23 ₆	17.14 ₇	20.50 ₈	27.77 ₂	35.92 ₈	44.75 ₁	54.26 ₄
50.245	14.16 ₁	16.88 ₁	20.29 ₀	27.52 ₂	35.56 ₇	44.11 ₁	53.46 ₂
61.204	13.92 ₀	16.68 ₂	20.06 ₄	27.22 ₁	35.18 ₈	43.63 ₂	52.94 ₇
72.036	13.75 ₁	16.51 ₀	19.85 ₅	26.96 ₄	34.88 ₅	43.18 ₇	52.36 ₃
83.503	13.56 ₂	16.28 ₄	19.59 ₇	26.61 ₆	34.47 ₄	42.85 ₅	52.01 ₂

Table 4

Molar conductivities $L/S \cdot \text{cm}^2 \cdot \text{mol}^{-1}$ LiBF_4 in propylene carbonate at temperatures 298.15–398.15 K

$\% \cdot 10^4$, $\text{mol} \cdot \text{kg}^{-1}$	298.15 K	308.15 K	318.15 K	328.15 K	338.15 K	358.15 K	378.15 K	398.15 K
2.850	–	33.02 ₅	38.87 ₅	45.20 ₁	51.70 ₆	65.33 ₅	79.02 ₇	91.76 ₄
4.332	27.25 ₉	32.85 ₄	38.76 ₈	45.06 ₈	51.41 ₈	65.03 ₃	79.24 ₅	91.48 ₆
6.130	27.40 ₃	32.69 ₂	38.62 ₉	44.85 ₉	51.38 ₃	64.67 ₉	–	90.67 ₉
8.251	27.20 ₂	32.52 ₅	38.43 ₀	44.61 ₅	50.98 ₆	64.25 ₂	77.88 ₈	89.82 ₄
10.189	27.19 ₁	32.42 ₅	38.41 ₀	44.54 ₂	50.95 ₅	64.23 ₃	77.20 ₆	89.28 ₅
13.295	27.03 ₇	32.31 ₆	38.24 ₆	44.28 ₆	50.70 ₉	63.01 ₈	77.21 ₀	89.84 ₇
16.349	26.86 ₉	32.17 ₁	37.99 ₆	44.06 ₃	50.41 ₃	62.69 ₅	76.53 ₆	89.52 ₇
23.808	–	31.63 ₃	37.58 ₀	43.41 ₅	48.91 ₀	61.63 ₂	75.23 ₈	88.49 ₀
28.275	26.22 ₆	31.44 ₆	37.01 ₃	42.95 ₀	48.54 ₄	61.10 ₉	74.36 ₅	87.60 ₂
33.215	26.06 ₉	31.23 ₃	36.77 ₉	42.66 ₂	48.01 ₆	60.75 ₉	–	86.93 ₀
37.850	26.10 ₁	31.10 ₃	36.53 ₆	42.41 ₈	48.45 ₉	60.41 ₉	73.10 ₉	–
43.455	25.57 ₈	30.67 ₁	–	41.81 ₂	47.37 ₃	60.04 ₅	72.43 ₅	85.64 ₇
48.826	25.58 ₇	30.66 ₆	36.10 ₁	41.84 ₃	47.35 ₀	59.71 ₂	72.43 ₁	–
55.023	25.43 ₄	30.50 ₉	36.00 ₄	41.58 ₆	47.31 ₁	59.64 ₂	72.14 ₀	85.12 ₉

Table 5

Molar conductivities $L/S \cdot \text{cm}^2 \cdot \text{mol}^{-1}$ Et_4NBF_4 in propylene carbonate at temperatures 278.15–398.15 K

$\% \cdot 10^4$, $\text{mol} \cdot \text{kg}^{-1}$	278.15 K	298.15 K	318.15 K	338.15 K	358.15 K	378.15 K	398.15 K
1.571	19.89 ₀	30.83 ₉	43.48 ₆	57.52 ₁	72.49 ₆	88.25 ₉	104.3 ₁
2.550	19.87 ₆	30.76 ₅	43.43 ₁	57.32 ₂	72.35 ₄	88.51 ₇	104.3 ₀
3.608	19.88 ₁	30.81 ₆	43.46 ₉	57.34 ₅	72.63 ₁	88.45 ₀	104.5 ₂
5.379	19.65 ₂	30.49 ₃	43.05 ₇	56.94 ₀	71.86 ₈	87.69 ₁	103.6 ₁
6.229	19.59 ₃	30.41 ₇	42.95 ₁	56.68 ₀	71.72 ₄	87.00 ₆	103.4 ₁
7.889	19.54 ₁	30.34 ₀	42.79 ₄	56.40 ₉	71.47 ₈	86.76 ₇	103.0 ₄
9.982	19.44 ₃	30.21 ₈	42.59 ₇	56.25 ₆	71.17 ₃	86.45 ₇	102.8 ₄
11.708	19.39 ₇	30.13 ₂	42.51 ₄	56.17 ₉	71.03 ₇	86.35 ₂	102.7 ₀
13.841	19.33 ₂	30.06 ₃	42.38 ₂	55.87 ₉	70.73 ₄	85.93 ₉	102.2 ₄
16.361	19.27 ₆	29.93 ₄	42.23 ₁	55.77 ₆	70.48 ₇	85.62 ₄	101.6 ₃
20.769	19.21 ₁	29.83 ₉	42.07 ₀	55.60 ₄	70.84 ₂	85.35 ₂	101.4 ₄
25.930	19.04 ₂	29.55 ₉	41.67 ₈	55.48 ₀	69.63 ₃	84.28 ₈	100.5 ₁
32.681	18.89 ₂	29.38 ₅	41.38 ₄	55.41 ₄	69.96 ₆	83.81 ₀	99.97 ₈
41.371	18.75 ₄	29.13 ₄	41.06 ₄	55.11 ₂	69.95 ₄	83.24 ₅	99.24 ₃
59.721	18.41 ₈	28.64 ₃	40.37 ₀	53.25 ₀	67.41 ₅	81.99 ₃	97.71 ₇

3.1. Processing of Experimental Results

To define constant of ionic association (K_A), limiting molar electrical conductivity (Λ_0) and parameter of the closest approach of ions (R) according to the experimental conductometric data (Tables 3-5), the method of processing of experimental data [28] was used. It consists in minimization of the function:

$$Q = \sum_{j=1}^k \left[\Lambda_j^{\text{exp}} - \Lambda_j^{\text{th}}(c_j^{\text{st}}; X) \right]^2 \Rightarrow \min. \quad (7)$$

with a vector of unknown parameters:

$$C = C(\Lambda_0, K_A, R) \quad (8)$$

From the mathematical point of view, the problem of finding of a vector with unknown parameters (8) for a case of symmetric electrolytes with unequal 1st degree of dissociation consists in solving the overflowed system of nonlinear equations: concentration dependence of molar electrical conductivity for a set of k concentrations (9), the law of mass action (10), material balance (11) and expressions for mean ionic coefficients of activity (12):

$$\Lambda_j = c_j f(c_j, \Lambda_0, R) / c_j^{\text{st}}, \quad j = \bar{1}, \bar{k} \quad (9)$$

$$K_A = c_j^0 / c_j^2 y_{+,-,j}^2 \quad (10)$$

$$c_j^0 + c_j = c_j^{\text{st}} \quad (11)$$

$$y_{+,-,j} = j(c_j, R) \quad (12)$$

where $c_j, c_j^0, c_j^{\text{st}}$ – concentration of ions, ionic pairs and stoichiometric concentration of electrolytes, respectively, and for non-associated electrolytes – $c_j^{\text{st}} \equiv c_j^i$.

For calculations of electric conductivity we chose the following combination of equations: the second approach of the Debye-Hückel theory (DH2) for coefficients of activity and the Lee-Wheaton equation [29] in the modification of Pethybridge [30] (LWP) for electrical conductivity (Eqs. (13) and (14), respectively) were used.

$$\ln y_{\pm} = -\frac{1}{2} lk / (1 + kR) \quad (13)$$

$$\Lambda = \Lambda_0 \left[1 + C_1(x) \cdot (lk) + C_2(x) \cdot (lk)^2 + C_3(x) \cdot (lk)^3 \right] - \frac{rk}{1+x} \left[1 + C_4(x) \cdot (lk) + C_5(x) \cdot (lk)^2 + x/12 \right] \quad (14)$$

where $r = 1.640214 \cdot 10^{-8} / h_0$, and C_1 – C_5 – complex functions of x .

Taking into account that LiClO_4 is a non-associated electrolyte, the data on these solutions were processed without considering the ionic association by the method of optimization of parameters $\{\Lambda_0, R\}$, where R – parameter of the closest approach of ions. For all other electrolytes, optimization by two parameters $\{\Lambda_0, K_A\}$ was used, parameter R was fixed as a constant value:


$$R = r^+ + r^- + nd_s \quad (15)$$

where r^+, r^- – radii of cation and anion, respectively, d_s – diameter of a molecule of the solvent; for alkali salts $n = 1$, for tetraalkylammonium salts $n = 0$.

Results of optimisation of 1-1 electrolytes in PC are given in Table 6 (at 298.15 K the literature data for Λ_0 and K_A are cited).

3.2. Discussion

For separation of Λ_0 into ionic components it was suggested that the ratio $I^i_o(\text{Bu}_4\text{N}^+) / I^i_o(\text{BPh}_4^-)$ was constant at all temperatures. It should be noted that this suggestion does not require to assume that $I^i_o h = \text{const}$, where h is the solvent density. Thus, Λ_0 values of the studied salts were separated into ionic components in accordance with the following scheme:



Results are given in Table 7 (for the ions at 298.15 K, the literature values are cited). As the Table shows, limiting molar ionic conductivities obtained indirectly from our data are well agreed with the literature data at 298.15 K.

Recently O. Kalugin *et al.* [31, 32] suggested to use the experimental ionic friction coefficients, $z = |z| eF / I^i_o$, to calculate a new quantitative description of ion-molecular interaction, the product $(g_K g_D)_{ef}$, where g_K and g_D are the modified Kirkwood factor [33] and Debye parameter [34]. According to [33, 34], the effective radius of Hubbard-Onsager dielectric friction theory [35, 36], R_{ho}^{ef} , is related to the experimental friction coefficient $z = f(r_i / R_{ho}^{\text{ef}})$, where r_i is own ionic radius. On the other hand, R_{ho}^{ef} may be expressed as a function of $(g_K g_D)_{ef}$ as [37]:

$$R_{ho}^{\text{ef}} = \left\{ \frac{(ze m_v)^2}{12(4pe_0 k_B T)^2} \cdot \frac{(e_\infty + 2)^2}{e(2e + e_\infty)} \cdot (g_K g_D)_{ef} \right\}^{1/4} \quad (16)$$

where m_v , e and e_∞ are the molecular dipole moment, dielectric constant of a solvent and dielectric constant at the infinite frequency, respectively.

Eq. (16) allows to obtain the product of two structure-sensitive quantities, g_K and g_D , from the experimental data for the ionic friction coefficient. For a pure solvent, these parameters are given by the well-known formulas [33, 34]:

$$(e - e_\infty) = \frac{m_v^2 g_K}{(4pe_0) 3k_B T a^3} \cdot \frac{e(e_\infty + 2)^2}{2e + e_\infty} \quad (17)$$

$$t_D = g_D \frac{4pa^3 h}{k_B T} \quad (18)$$

where t_D is the dielectric relaxation time and a is the molecular radius calculated from the molecular volume.

Table 6

Results of conductivity measurements for 1-1 electrolytes in propylene carbonate ($\Lambda_0/S \times \text{cm}^2 \text{mol}^{-1}$, $K_A/\text{dm}^3 \text{mol}^{-1}$, R/nm , $s_L/S \times \text{cm}^2 \text{mol}^{-1}$)

T, K	Λ_0	K_A	R	s_L
LiClO₄				
298.15	26.87 ± 0.02 26.08(min) [3] – 28.0(max) [18]	0.47(min)[18]– 1.5(max)[13]	2.39 ± 0.04 2.80 ± 0.82 [23]	0.08
308.15	32.26 ± 0.02		2.38 ± 0.04	0.09
318.15	37.80 ± 0.03		2.40 ± 0.04	0.1
338.15	49.65 ± 0.07		1.56 ± 0.11	0.2
358.15	62.08 ± 0.07		1.04 ± 0.07	0.2
378.15	76.35 ± 0.08		0.65 ± 0.06	0.2
398.15	93.01 ± 0.10		0.33 ± 0.07	0.3
NaClO₄				
298.15	28.08 ± 0.02 27.29 [23] – 28.30 [31]	4.3 ± 1.8 0 [23] – 1.0 [32]	0.964 1.41 [23]	0.03
308.15	33.60 ± 0.07	6.9 ± 4.6	0.964	0.1
318.15	39.24 ± 0.03	6.9 ± 1.9	0.964	0.1
338.15	51.78 ± 0.08	9.5 ± 3.7	0.964	0.1
358.15	65.68 ± 0.08	15.6 ± 3.2	0.964	0.2
378.15	80.17 ± 0.13	15.6 ± 4.1	0.964	0.2
398.15	96.16 ± 0.27	16.5 ± 7.7	0.964	0.5
Bu₄NClO₄				
298.15	27.40 ± 0.01 27.42 [3] – 28.20 [23]	1.3 ± 0.1 0.2 [12] – 2.2 [3]	0.734 2.54 [23]	0.04
308.15	32.52 ± 0.02	0.9 ± 0.2	0.734	0.06
318.15	38.01 ± 0.02	1.4 ± 0.2	0.734	0.05
338.15	49.70 ± 0.11	1.6 ± 0.8	0.734	0.3
358.15	62.62 ± 0.03	3.2 ± 0.2	0.734	0.1
378.15	76.17 ± 0.04	4.5 ± 0.2	0.734	0.1
398.15	90.62 ± 0.04	5.9 ± 0.2	0.734	0.1
Bu₄NBPh₄				
298.15	17.57 ± 0.02 17.14 [23], 17.15[11], 17.31[12]	4.2 ± 0.4 0.93 [23] – 10.2 [12]	0.947 3.98 [23]	0.05
308.15	21.08 ± 0.05	8.5 ± 0.9	0.947	0.1
318.15	24.75 ± 0.04	6.8 ± 0.6	0.947	0.1
338.15	32.92 ± 0.05	7.2 ± 0.5	0.947	0.1
358.15	41.83 ± 0.06	8.1 ± 0.6	0.947	0.2
378.15	51.33 ± 0.09	9.4 ± 0.7	0.947	0.2
398.15	61.60 ± 0.11	10.2 ± 0.7	0.947	0.3
LiBF₄				
298.15	28.21 ± 0.07 28.48[15] – 28.83 [22]	8.37 ± 1.25 1.3 [22] – 10.1 [15]	0.941	0.2
308.15	33.74 ± 0.04	8.35 ± 0.55	0.941	0.08
318.15	39.85 ± 0.07	9.09 ± 0.91	0.941	0.1
328.15	46.29 ± 0.07	11.1 ± 0.7	0.941	0.1
338.15	52.95 ± 0.16	14.9 ± 1.6	0.941	0.3
358.15	66.51 ± 0.16	15.7 ± 1.2	0.941	0.3
378.15	80.60 ± 0.17	16.7 ± 1.2	0.941	0.4
398.15	92.96 ± 0.19	19.7 ± 1.24	0.941	0.4
Et₄NBF₄				
278.15	22.18 ± 0.01	2.1 ± 0.2	0.632	0.01
298.15	33.33 ± 0.01 33.96 [22]	1.9 ± 0.2 0 – 3.0 [22]	0.632	0.02
318.15	46.21 ± 0.01	3.1 ± 0.2	0.632	0.03
358.15	75.64 ± 0.03	4.1 ± 0.4	0.632	0.03
378.15	91.32 ± 0.05	5.0 ± 0.3	0.632	0.09
398.15	107.95 ± 0.07	4.7 ± 0.3	0.632	0.1

Values of limiting molar conductivities of ions ($\lambda_0^{\dot{i}}$) in PC in a wide range of temperatures

T, K	Li^+	Na^+	Et_4N^+	Bu_4N^+	BF_4^-	ClO_4^-	BPh_4^-
298.15	8.512 (7.30 [3]– 8.89 [3,15])	9.722 (9.04–10.71 [12])	13.59 (11.53–13.58 [12])	9.042 (8.48 [12]– 9.39[3])	19.74	18.36 (18.43 [32]– 18.89 [31])	8.528 (8.10 [9])
308.15	10.47	11.82	14.08	10.73	25.03	21.79	10.34
318.15	12.33	13.77	15.15	12.54	31.06	25.47	12.21
338.15	16.35	18.48	17.89	16.40	43.41	33.30	16.53
358.15	21.13	23.73	19.48	20.66	56.16	41.96	21.17
378.15	25.32	29.14	21.78	25.14	69.54	51.03	26.19
398.15	32.30	35.44	27.04	29.90	80.91	60.72	31.70

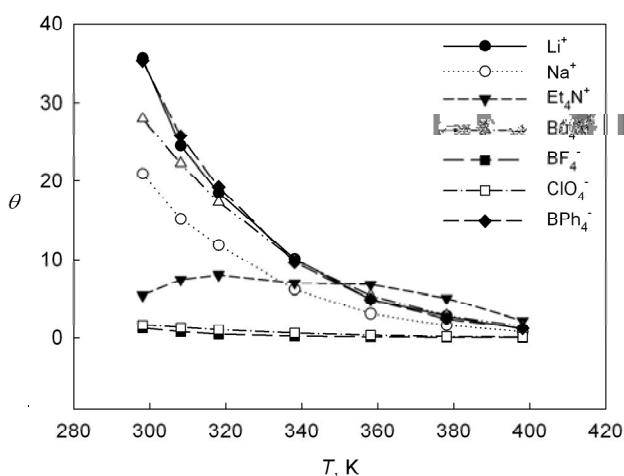


Fig. 1. Dependence of the values q of several ions with the same charge in PC on temperature

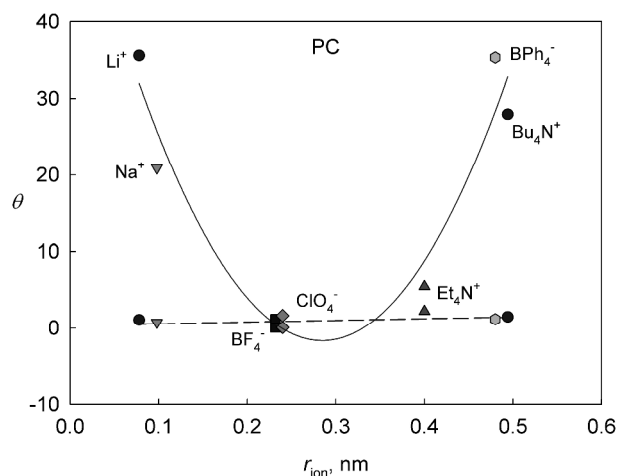


Fig. 2. Dependence of values q of several ions with the same charge in PC on radii of ions at 298 and 398 K

Then, in accordance with Samoilov's approach, the ratio

$$q = (g_k g_D)^{ef} / (g_k g_D) \quad (19)$$

was suggested as a measure of ion's influence on the structure and molecular dynamics of a solvent, as the parameter of solvation microdynamics. The value $(g_k g_D)_0$ corresponds to the pure solvent and can be calculated using Eqs. (19, 20) from the physical properties of a solvent. Values $Q > 1$ correspond to structure-making effect of an ion and decrease of molecules activity in its vicinity, and vice versa for $Q < 1$.

The data on the dielectric relaxation time, t_D , taken from [38], is described by:

$$t_D = 5.294 - 0.052 \cdot t + 1.83 \cdot 10^{-4} \cdot t^2. \quad (20)$$

and e_V was calculated from the Clausius-Mosotti equation [39]

$$P = \frac{e_\infty - 1}{e_\infty + 2} \cdot \frac{M}{d} \quad (21)$$

assuming that the deformational polarization P is independent from temperature.

Fig. 1 shows the temperature dependence of q , and Fig. 2 shows the dependence of q for single-charged ions in PC on the ionic radius. The Li^+ ion has rather high values of q , this ion sufficiently slows down the motion of the nearest solvent molecules. As Fig. 1 shows, the values of the parameter q for the lithium ion in PC practically coincide with the values of the parameter q of the BPh_4^- and Bu_4N^+ ions and decrease considerably with the increase of the temperature. It can be connected with the fact that the size of the lithium ion in a solvation shell practically does not differ from the size of ions BPh_4^- and Bu_4N^+ . It points to a large positive solvophobic ability of BPh_4^- and Bu_4N^+ in PC, while the values of the parameter q practically do not change with the increase of the temperature for BF_4^- , ClO_4^- and Et_4N^+ .

Fig. 2 shows the dependence of the parameter q on the size of the ion at 298.15 and 398.15 K. As Fig. 2 shows, the values of q for Li^+ and Na^+ (at 298.15 K) are much higher than 1, which points to solvophilic solvation of these ions in PC, whereas the values of q for the anions BF_4^- , ClO_4^- and Et_4N^+ are almost equal to 1, which points

to the poor solvation of these ions in PC. Meanwhile, the parameters q for all ions at 398.15 K are almost equal to 1.

These results can be interpreted as follows. In general, influence of the ions on the nearest solvation dynamics may be represented by two components: solvophilic and solvophobic [40]. The first one is related to the ion's action on the solvent by the electrical field of the ion. Solvophilic solvation, depending on the ionic radius and the solvent structure features (presence of cavities, nature of intermolecular interaction and molecular motion, *etc.*), can be either positive or negative. Solvophobic solvation is observed for the ions of large radii only as an obstacle effect: motion of the solvent molecules becomes slower, because part of the solution space is occupied by the ion itself and is inaccessible for the solvent molecules. Solvophobic solvation increases with the increasing ionic radius and decreases with the increase of the temperature.

The obtained values and dependences of q on temperature and radii of ions are confirmed by the data obtained from the spectral characteristics.

Association of the molecules has considerable impact on the properties of liquids and solutions and the kinetics of the processes occurring in them. In the work [41] investigations of the nature of self-association of molecules of liquid propylene carbonate using the method of spectral combinational dispersion of light was performed. The work shows that PC has more stable cyclic dimers as in it both atoms of the carbonyl group participate in the intermolecular interaction, while in a chain-like dimer the interaction occurs only through one of them. As there are more chain dimers in PC, they collapse faster with the increase of temperature. From the work [42] the conclusion is drawn that absorption bands corresponding to the vibrations with the participation of atoms of the C=O bond of the carbonyl group of PC appeared to be the most sensitive to the ion-molecular interaction. Considering that the greatest density of a negative charge in the PC molecule is concentrated on the atom of oxygen of the C=O fragment, it is possible to draw a conclusion that the interaction of the PC molecules with cations of the dissolved salts occurs through an atom of oxygen of the group C=O and is followed by the cleavage of dipole-dipole associates formed in the liquid PC. In a series of cations Na-Li-Mg in PC strengthening of interaction of the corresponding cations with PC molecules is observed, and as a consequence – decrease of frequencies of the absorption bands.

According to the results of spectral studies of both pure solvent and solutions of 1-1 electrolytes in PC, as well as the obtained values and dependences of the parameter q , assumption of poor solvation of anions in PC is confirmed.

4. Conclusions

Conductometric investigation of several 1-1 electrolytes in PC was performed in a wide range of temperatures. The values of limiting molar electrical conductivity (LMEC) Λ_0 and association constants K_A were calculated, which are in good agreement with the data for 298.15 K reported in literature.

The values of LMEC λ_0^i in the wide range of temperatures were obtained for the first time using the indirect method of separation into ionic components. The λ_0^i values are also in good agreement with the data for 298.15 K found in literature.

The assumption about the poor solvation of the ions in PC is confirmed. It was found that Li⁺ ion in its solvation shell does not concede to the B_u₄N⁺ and BPh₄⁻ ions.

It was confirmed that at high temperatures (> 333 K) all ions virtually have no solvation shells (for Li⁺ it is destroyed upon increase of the temperature).

The values of LMEC for the ions can be used for more thorough investigation of the interparticle interactions in solutions.

References

- [1] Xu K.: Chem. Rev., 2004, **104**, 4303.
- [2] Lvov A.: Sorovsky Osvitniy Zh., 2001, **7**, 45.
- [3] Jansen M. and Yeager H.: J. Phys. Chem., 1973, **77**, 3089.
- [4] McDonagh P. and Reardon J.: J. Solut. Chem., 1996, **25**, 607.
- [5] Barthel J., Gores H.-J. and Kramp L.: J. Phys. Chem., 1996, **100**, 3671.
- [6] Safonova L., Pacaciya B. and Kolker A.: Zh. Fiz. Khimii, 1994, **62**, 262.
- [7] Mukherjee L., Boden D. and Lindauer R.: J. Phys. Chem., 1970, **74**, 1942.
- [8] Koshel N., Likhina A., Pinielle I. *et al.*: Elektrokhim., 1986, **22**, 1181.
- [9] Salomon M. and Plichta E.: Electrochim. Acta, 1984, **29**, 731.
- [10] Reardon J.: Electrochem. Acta, 1987, **32**, 1595.
- [11] Salomon M. and Plichta E.: Electrochim. Acta., 1983, **28**, 1681.
- [12] Salomon M. and Plichta E.: Electrochim. Acta., 1985, **30**, 113.
- [13] Mishustin A.: Zh. Fiz. Khimii, 1996, **70**, 836.
- [14] Webber A.: J. Electrochem. Soc., 1991, **138**, 2586.
- [15] Christie A. and Vincent C.: J. Phys. Chem., 1996, **100**, 4618.
- [16] D'Aprano A., Salomon M. and Iammarino M.: J. Electroanal. Chem., 1996, **403**, 245.
- [17] Barthel J., Gores H. and Schmeer G.: Ber. Bunsenger Phys. Chem., 1979, **83**, 911.
- [18] Hojo M., Miyauchi Y., Tanio A. *et al.*: J. Chem. Soc. Faraday Trans., 1991, **87**, 3847.
- [19] Miyauchi Y., Hojo M., Moriyama H. *et al.*: J. Chem. Soc. Faraday Trans., 1992, **88**, 3175.
- [20] Catul J., Angel J., Maneeley H. *et al.*: J. Electrochem. Soc., 1975, **122**, 319.
- [21] He X. *et al.*: J. Phys. Chem. B., 2005, **109**, 23141.
- [22] Ue M.: J. Electrochem. Soc., 1994, **141**, 3336.

- [23] Schmelzer N., Einfeldt J. and Grigo M.: *Wiss. Z. UNI ROSTOCK*, 1990, **39**, 41.
- [24] Zana R., Desnoyers J., Perron G. *et al.*: *J. Phys. Chem.*, 1982, **86**, 3996.
- [25] Krumgalts B.: *J. Chem. Soc. Faraday Trans. I.*, 1983, **79**, 571.
- [26] Barthel J., Wahter R. and Gores H.-J.: *Mod. Aspects Electrochem.*, 1979, **13**, 18.
- [27] Barthel J., Feuerlein F., Neueder R. *et al.*: *J. Solut. Chem.*, 1980, **9**, 209.
- [28] Kalugin O. and Vyunnik I.: *Zh. Obsh. Khimii*, 1989, **59**, 1628.
- [29] Lee W. and Wheaton R.: *J. Chem. Soc. Faraday Trans II.*, 1978, **74**, 743.
- [30] Pethybridge A. and Taba S.: *J. Chem. Soc. Faraday Trans I.*, 1980, **76**, 368.
- [31] Kalugin O. and Vyunnik I.: *Zh. Khim. Fiziki*, 1991, **10**, 708.
- [32] Kalugin O., Vyunnik I. and Nur-Eddin I.: *Zh. Strukt. Khimii*, 1992, **33**, 105.
- [33] Frohlich G.: *Theory of Dielectrics*, Clarendon Press, Oxford 1949.
- [34] Evans D., Tominaga T., Hubbard J. *et al.*: *J. Phys. Chem.*, 1979, **83**, 2669.
- [35] Hubbard J. and Onsager L.: *J. Chem. Phys.*, 1977, **67**, 4850.
- [36] Hubbard J.: *J. Chem. Phys.*, 1978, **68**, 1649.
- [37] Kalugin O., Lebed A. and Vyunnik I.: *J. Chem. Soc. Faraday Trans.*, 1998, **94**, 2103.
- [38] Payne R. and Theodorow I.: *J. Phys. Chem.*, 1972, **76**, 2892.
- [39] Usacheva T. and Shakhparonov M.: *Sovr. Problemy Fiz. Khimii*, 1980, **12**, 259.
- [40] Rodnikova M.: *Zh. Fiz. Khimii*, 1993, **67**, 275.
- [41] Pereligin I., Itkulov I. and Krauze A.: *Zh. Fiz. Khimii*, 1992, **66**, 573.
- [42] Pereligin I., Klimchuk M. and Smolskaya E.: *Zh. Fiz. Khimii*, 1987, **41**, 101.

**ЕЛЕКТРИЧНА ПРОВІДНІСТЬ
ТА МІЖЧАСТИНКОВІ ВЗАЄМОДІЇ В РОЗЧИНАХ
1-1 ЕЛЕКТРОЛІТІВ В ПРОПІЛЕНКАРБОНАТІ
У ШИРОКОМУ ІНТЕРВАЛІ ТЕМПЕРАТУР**

Анотація. Представлено результати кондуктометричного дослідження розчинів деяких 1-1 електролітів у пропіленкарбонаті в інтервалі температур 298–398 К. З використанням розширеного рівняння електричної провідності Лі-Уїтона визначено константи йонної асоціації. Встановлено, що LiClO_4 в пропіленкарбонаті є неасоційованим електролітом. Для врахування динаміки йонної асоціації проведено поділ на йонні складові електричної провідності в широкому інтервалі температур.

Ключові слова: пропіленкарбонат, електрична провідність, асоціація, 1-1 електроліти.