

Bohdan Trembach¹, Aleksandr Grin², Illia Trembach³¹ Welding Technology Department, Donbas State Engineering Academy,
72, Academic Str., Kramatorsk, Ukraine,Private Joint Stock Company “Novokramatorsky Mashinostroitelny Zavod”, 5, Ordzhonikidze Str.,
Kramatorsk, Ukraine, e-mail: btrembach89@gmail.com, ORCID: 0000-0002-2305-8411² Welding Technology Department, Donbas State Engineering Academy,
72, Academic Str., Kramatorsk, Ukraine, e-mail: mf@dgma.donetsk.ua, ORCID: 0000-0002-3432-8149³ Private Joint Stock Company “Novokramatorsky Mashinostroitelny Zavod”, 5, Ordzhonikidze Str.,
Kramatorsk, Ukraine, e-mail: i_trembach@ukr.net, ORCID: 0000-0002-3932-2520

STUDY OF THE INFLUENCE OF THE ADDITION OF AN EXOTHERMIC MIXTURE AND THE RATIO OF THE COMPONENTS OF THE EXOTHERMIC MIXTURE ON THE MELTING INDICES AT FCAW

Received: May 19, 2020 / Revised: July 29, 2020 / Accepted: July 31, 2020

© Trembach B., Grin A., Trembach I., 2020

<https://doi.org/10.23939/ujmems2020.01.047>

Abstract. An important issue in the processes of strengthening and restoration of surfaces exposed to abrasive, abrasive-corrosive and hydroabrasive wear, using the process of self-protective flux-cored arc welding (FCAW), is to increase the productivity of hardfacing and the quality of the hardfacing metal. The literature review showed that one of the ways to increase the productivity of hardfacing and improve the quality of the hardfaced metal is to add an exothermic mixture to the core filler of flux-cored wire electrode. The effect of composition of filler core during FCAW on the fusion parameters, namely the addition of exothermic mixture (TM), the ratio of exothermic mixture components (CuO/Al), and the ratio of exothermic mixture oxidant to carbon content in the core composition (CuO/C) has been studied. It has been found that the optimum areas for the deposition rate (G_d), deposition factor (ad) and spattering factor (ψ_s) are observed for the following values of the core components: TM = 25...39, CuO/C = 5...6, CuO/Al = 3...4.

Keywords: hardfacing, FCAW-S, exothermic mixture, simplex-centroid design, deposition rate, deposition rate factor, spattering factor, composition.

Introduction

Mining and processing plants and mining companies in Ukraine and around the world annually spend thousands of tons of metal on the manufacture of spare parts to replace wear parts. Regarding the conditions and the intensity of the wear processes are integral part of the instruments lifetime and reliability as well as of the whole systems. Hardfacing of parts is used to increase service life, manufacturability, and reduce production costs [1]. Throughout the diversity of reinforcement and restoration processes, the use of flux-cored wires (FCAW) has become widespread. When hardfacing FCAW, as well as FCAW-S, obtaining the hardfacing metal of a given chemical composition, the required quality (in the content of non-metallic inclusions), as well as high technical and economic performance of the works (deposition rate and deposition rate factor) play an important role [2], [3], [4]. At the same time, the most important characteristics of deposition technologies are: deposition rate, deposition rate factor and the spattering factor [2]–[5].

Problem Statement

During the melting of flux-cored wires, due to the lag of the melting of the core from the metal wire sheath, a protrusion of the core is formed at the end of the flux-cored wire. This protrusion can be destroyed with the formation of large particles, which, when they enter the molten bath without having to

melt, can cause exogenous inclusions [6]. In addition, the lag of the melting of the core from the metal wire sheath, which causes deterioration of the welding performance and reduces the effectiveness of protection of weld metal from the air [2], [7]. One way to ensure uniformity of melting of the FCAW is to introduce into the core filler of the exothermic mixture [4], [8], [9].

Review of Modern Information Sources on the Subject of the Paper

The most common exothermic systems are Fe₂O₃-Al, Fe₂O₃-Ti [10], while the CuO-Al system is of great interest [8], due to the greatest thermal effect, which makes it possible to exclude the possibility of the charge entering the weld bath when a smaller amount of exothermic is introduced, which makes it possible to achieve a higher degree of doping of weld metal. In addition, when using thermal mixtures of other systems, such as CuO, due to the reduction of the oxidant, the latter enters the metal, thereby doping it, which provides an even higher level of doping [8].

It is known that alloys with high carbon content are used for hardfacing of abrasive and hydro-abrasive wear parts [12]. It is known that the recovery of copper oxide in exothermic mixtures can occur both aluminium and carbon. In this case, the degree and completeness of recovery by a particular reducing agent will depend on the ratio of components in the FCAW-S charge at constant other parameters. In the modern literature there is no data on the study of the influence of the ratio of the components of the core filler, namely the components of the exothermic mixture CuO-Al and carbon. Thus, it is of considerable interest to study the effect of components of the exothermic mixture on the melting indices of the FCAW-S, to determine the optimal ratio of oxidant to the reducing agents of aluminium and carbon, as well as the optimal amount of exothermic mixture.

The objective of the paper. Determination of the nature of the effect and optimal values of the amount of exothermic mixture (TM), and the ratio of CuO/Al and CuO/C in the composition of FCAW-S filler on the qualitative indicators of its fusion using simplex-lattice design.

Materials and methods

To investigate the effect of FCAW-S core composition on fusion rates, a standard three-factor simplex-centroid design has been selected. Experiments are being conducted to investigate the effect of filler components (amount of exothermic mixture) on the deposition rate (G_d), deposition rate factor (a_d) and spattering factor (ψ_s). The design in coded values is shown in Table 1. To transmit from the simplex coordinate system to the natural values of the factors the following formulae are used Eq. 1–3:

$$(CuO/C) = 3 + 3 \times x_1 ; \tag{1}$$

$$(CuO/C) = 3 + 3 \times x_2 ; \tag{2}$$

$$(TM) = 25 + 40 \times x_3 . \tag{3}$$

The design represented in natural values is also given in Table 1.

Table 1

Three-factor simplex-centroid experiment design

No.	Code values			Actual values		
	x ₁	x ₂	x ₃	CuO/C	CuO/Al	TM, %
1	0	1	0	3.00	6.00	25
2	0.333	0.333	0.334	4.00	4.00	35
3	0.667	0.333	0	5.00	4.00	25
4	0	0.667	0.333	3.00	5.00	35
5	0.333	0	0.667	4.00	3.00	45
6	0.5	0.25	0.25	4.50	3.75	32.5
7	0.25	0.25	0.5	3.75	3.75	40
8	0.25	0.5	0.25	3.75	4.50	32.5
9	0.333	0.667	0	4.00	5.00	25

According to the experiment design matrix experimental wires have been produced the cores of which comprised components which composition is given in Table 2.

Table 2

Composition of S-FCAW, %

Experimental composition		1	2	3	4	5	6	7	8	9
The name of the component										
Gas slag creating	Fluorspar GOST 4421-73	24	21	24	21	21	24	21	24	24
	Rutilovy concentrate GOST 22938-78									
	Calcium carbonate GOST 8252-79									
Alluring and deoxidizers	Titanium powder PTM TU 14-22-57-92	41	41	41	41	34	41	38	41	41
	Ferrosilicon FS-75 GOST 1415-78									
	Ferromanganese FMN-88A GOST 4755-91									
	Metal Chrome X99 GOST 5905-79									
	Ferovanadiy FVd-50 GOST 27130-94									
Graphite is silver		5.6	5.8	3.45	7.6	7.1	4.9	7	5.8	4.3
Oxide of copper powder-like GOST 16539 79		16.7	25	17.25	22.8	28.5	21.8	26	21.8	17.3
Aluminium powder PA1 GOST 6058-73		2.8	5.8	4.3	4.6	9.5	5.8	7	4.9	3.5
Iron powder PZr-1 GOST 9849-86		9.9	3.1	10	3	0	2.5	1	2.5	10

FCAW-S with exothermic mixture with a diameter of 4 mm have been made for the research. As a slag-forming component, a slag material has been used: marble-fluorite-rutile. Deposition has been performed by single-pass rollers on 10×100×200mm S 235 J2G2 EN 10025-2 (St3ps) low-carbon steel plates using a welding machine with a power source of constant voltage. Wire Filling Ratio: 0.34–0.35.

The technological characteristics of the melting of cored wires G_d , α_d and ψ_s , were calculated according to the following equation are used Eq. 4–6:

$$G_d = \frac{m_d \times 3600}{t}; \quad (4)$$

$$\alpha_d = \frac{G_d}{I_{asw}}; \quad (5)$$

$$y_s = \frac{m_m - m_s}{m_m} \times 100\%, \quad (6)$$

where m_m – the mass of molten electrode metal, g; m_d – the mass of deposited metal, g; m_s – the mass of spattering, g; t – surfacing time, sec; I_{asw} – welding current, Amp.

Results and Discussion

Results of the experiment and calculations (G_d^s , α_d^s , ψ_s^s) are given in Table 3.

The results of the analysis of the influence of factors on the deposition rate (G_d), deposition rate factor (α_d) and spattering factor (ψ_s) are given in Table 3.

Analysis of the design data obtained using Statistica (StatSoft) system [11]. The results of the model significance obtained using Statistica program for three fusion indices are shown in Fig. 1.

Table 3

Results of research

No.	Welding current I_{awc} , Amp	Deposition rate, g/h		Deposition rate factor, g/Amp-h		Spattering factor, %	
		Experimental, G_d^e	Calculated, G_d^s	Experimental, α_d^e	Calculated, α_d^s	Experimental, ψ_s^e	Calculated, ψ_s^e
1	353.48	4.192	4.182	11.860	11.636	14.35	14.35
2	356.9	4.686	4.765	13.130	12.210	9.90	9.90
3	357.3	4.655	4.631	13.027	12.938	14.95	14.95
4	372.22	4.590	4.604	12.331	12.643	13.62	13.62
5	370.8	3.972	3.989	10.711	11.022	20.84	20.84
6	380.58	4.806	4.847	12.628	12.875	9.74	9.74
7	407.47	4.769	4.564	11.704	11.751	10.75	10.75
8	395.85	4.654	4.706	11.756	12.000	10.85	10.85
9	395.7	4.228	4.214	10.685	10.958	20.27	20.27
10	372.6	3.844	3.893	10.317	10.116	17.94	17.38

Overall Fit of Model; Var.: G_d , kg/h (CuO-C-Al-%TM) 3 Factor mixture design; Mixture total=1., 10 Runs					
Source	SS	df	MS	F	p
Model	1.023849	6	0.170641	8.966086	0.049807
Total Error	0.057096	3	0.019032		
Total Adjusted	1.080944	9	0.120105		

Overall Fit of Model; Var.: α_d , g/Ah (CuO-C-Al-%TM) 3 Factor mixture design; Mixture total=1., 10 Runs					
Source	SS	df	MS	F	p
Model	8.448603	6	1.408100	4.166067	0.134486
Total Error	1.013978	3	0.337993		
Total Adjusted	9.462581	9	1.051398		

Overall Fit of Model; Var.: ψ_p , % (CuO-C-Al-%TM - Показ) 3 Factor mixture design; Mixture total=1., 10 Runs					
Source	SS	df	MS	F	p
Model	144.6512	6	24.10853	16.44746	0.021394
Total Error	4.3974	3	1.46579		
Total Adjusted	149.0486	9	16.56095		

Fig. 1. Results of calculating the significance of the model by the residual sum of the squares: a – deposition rate (G_d); b) deposition rate factor (α_d); c) spattering factor (ψ_s)

Statistically significant effects are observed when $p < 0.05$ is a Student's test. Analyzing the data obtained, we can conclude that the models obtained are significant.

$$G_d = 5.89299 \times x_1 + 4.20769 \times x_2 + 3.17881 \times x_3 - 3.06163 \times x_1 \times x_2 - 0.34053 \times x_1 \times x_3 + 2.97135 \times x_2 \times x_3 + 10.67538 \times x_1 \times x_2 \times x_3; \tag{7}$$

$$a_d = 19.4971 \times x_1 + 11.91117 \times x_2 + 9.1192 \times x_3 - 17.9461 \times x_1 \times x_2 + 8.5066 \times x_1 \times x_3 + 5.1104 \times x_2 \times x_3 + 36.6739 \times x_1 \times x_2 \times x_3; \tag{8}$$

$$y_s = 0.2097 \times x_1 + 14.487 \times x_2 + 22 \times x_3 - 46.4368 \times x_1 \times x_2 + 28.036 \times x_1 \times x_3 - 16.2571 \times x_2 \times x_3 - 237.7167 \times x_1 \times x_2 \times x_3. \tag{9}$$

When turning the simplex coordinate system to the natural values of the factors we get the following equation:

$$G_d = - 15.105 + 3.888 \times (\text{CuO/C}) + 2.1714 \times (\text{CuO/Al}) + 0.1508 \times (\text{TM}) - 0.7922 \times (\text{CuO/C}) \times (\text{CuO/Al}) - 0.0601 \times (\text{CuO/C}) \times (\text{TM}) - 0.029 \times (\text{CuO/Al}) \times (\text{TM}) + 0.024 \times (\text{CuO/C}) \times (\text{CuO/Al}) \times (\text{TM}); \tag{10}$$

$$a_d = 19.4971 \times x_1 + 11.91117 \times x_2 + 9.1192 \times x_3 - 17.9461 \times x_1 \times x_2 + 8.5066 \times x_1 \times x_3 + 5.1104 \times x_2 \times x_3 + 36.6739 \times x_1 \times x_2 \times x_3; \tag{11}$$

$$y_s = 0.2097 \times x_1 + 14.487 \times x_2 + 22 \times x_3 - 46.4368 \times x_1 \times x_2 + 28.036 \times x_1 \times x_3 - 16.2571 \times x_2 \times x_3 - 237.7167 \times x_1 \times x_2 \times x_3. \tag{12}$$

The resulting response surface simulations and contour plots are shown in Fig. 2.

Study of the Influence of the Addition of an Exothermic Mixture and the Ratio of the Components ...

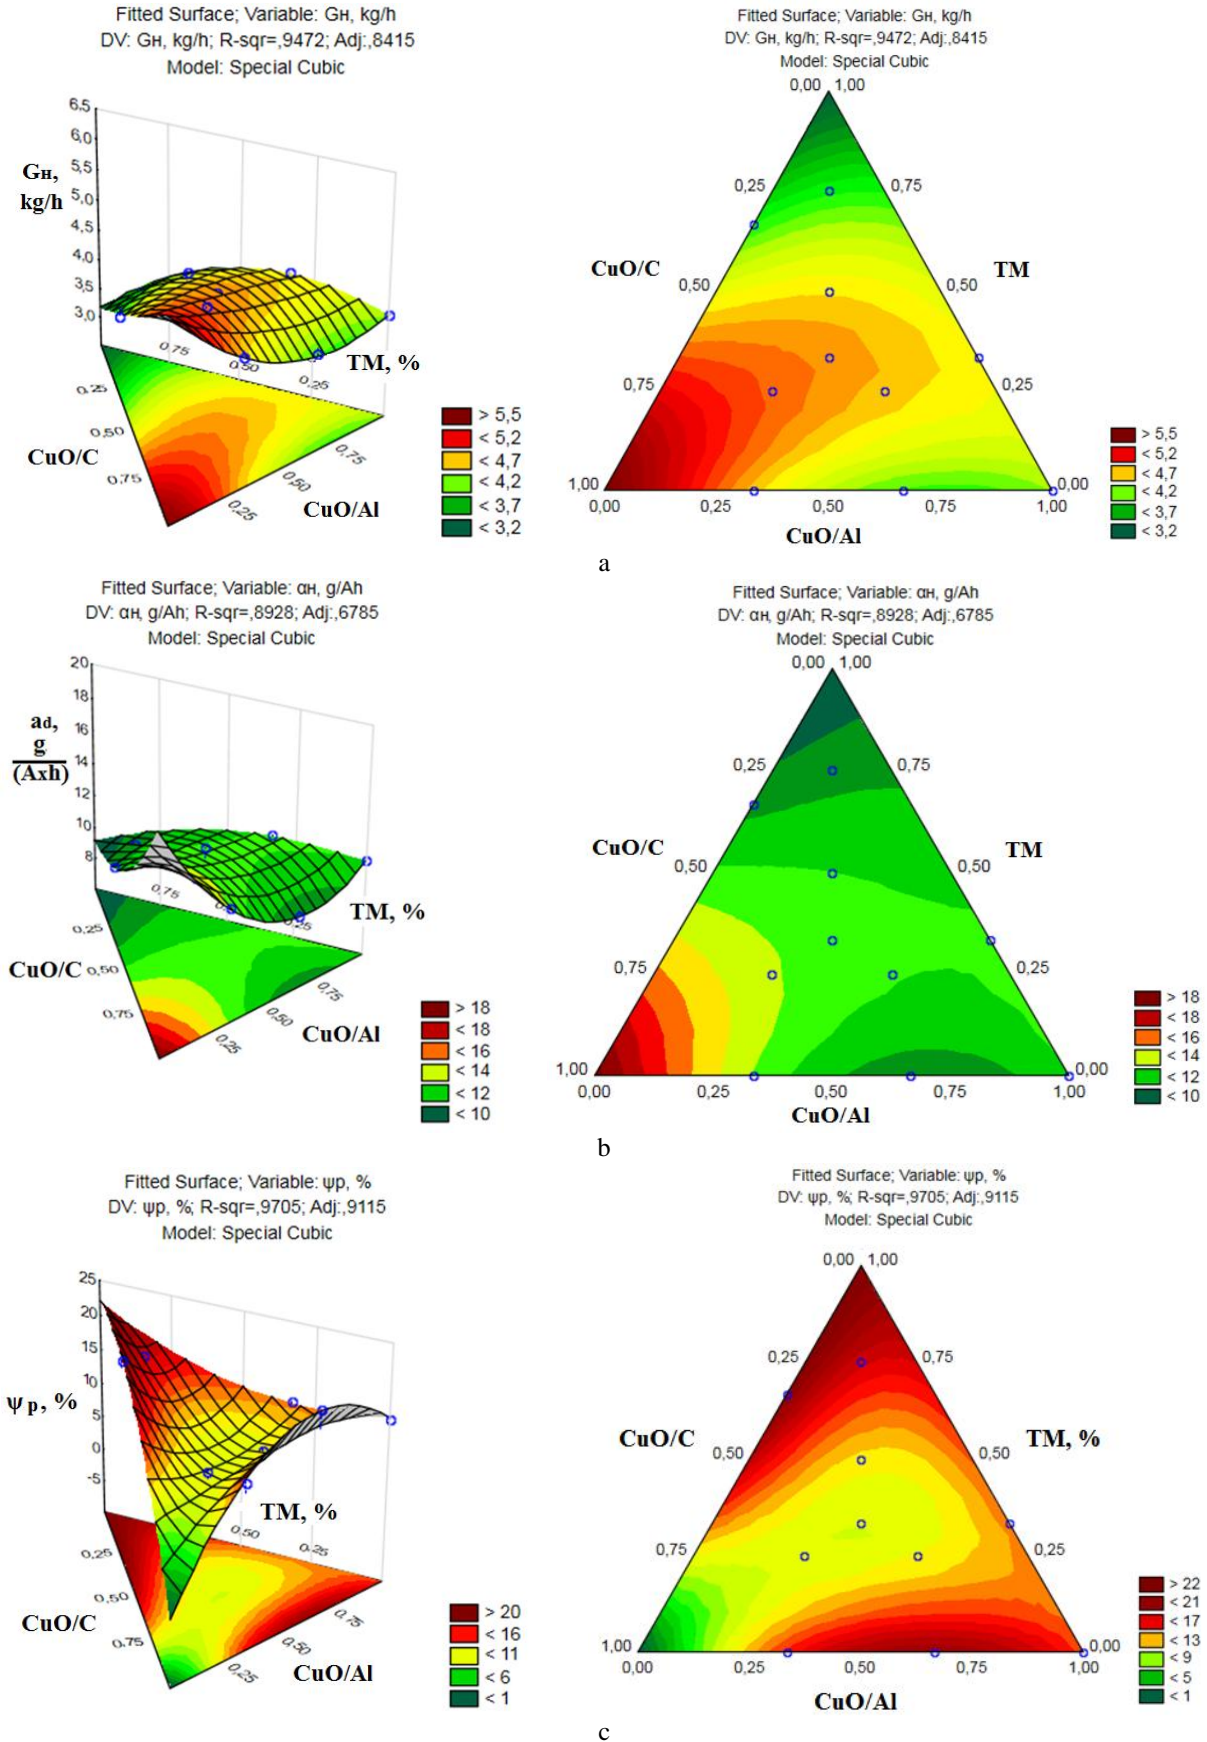


Fig. 2. Response surface and color contour plot depending on exothermic mixture (TM) content, ratios (CuO/C) and (CuO/Al) for melting ratios: a – deposition rate (G_d); b – deposition rate factor (α_d); c – spattering factor (ψ_s)

The highest values of deposition rate according to the results of the study depending on the response surfaces and contour plot (see Fig. 2, a) of the mathematical model (Eq. 10) correspond to the minimum amount of exothermic mixture (0...0.30, respectively) of the total fraction of the FCAW-S core, high ratios of CuO/C = 5...6 (code values 0.6...1), and low ratio CuO/Al = 3...4 (code values 0...0.25). That is, in order to achieve high deposition rates in the composition of the flux wire, the amount of aluminum over the percentage of silver (carbon) graphite must prevail.

For deposition rate factor (α_d), the obtained dependencies are retained. According to the response surfaces and the contour plot obtained (Fig. 2, b), as well as the model obtained in natural equation (Eq. 11), the following values of the variable parameters correspond to the highest values of the deposition rate factor (α_d): TM = 25...39 (code values 0...0.34); CuO/C = 5...6 (code values 0.6...1); CuO/Al = 3...4 (code values 0...0.33).

The analysis of the response surfaces obtained (Fig. 2, c) shows that the spattering loss factor (ψ_s) decreases with increasing of Cu/C ratio, i.e. decrease in carbon (silver graphite) in the FCAW-S core composition, and decrease in CuO/Al ratio. Technologically acceptable indicators are achieved at the following values: TM = 25...45 (code values 0...0.5); CuO/C = 4.5...6 (code values 0.5...1); CuO/Al = 3...4.5 (code values 0...0.5).

The interpretation diagram of the imposition of certain areas of optimal values (Fig. 3) provides an opportunity to determine the optimal limit of the complex effect of the factors under the study.

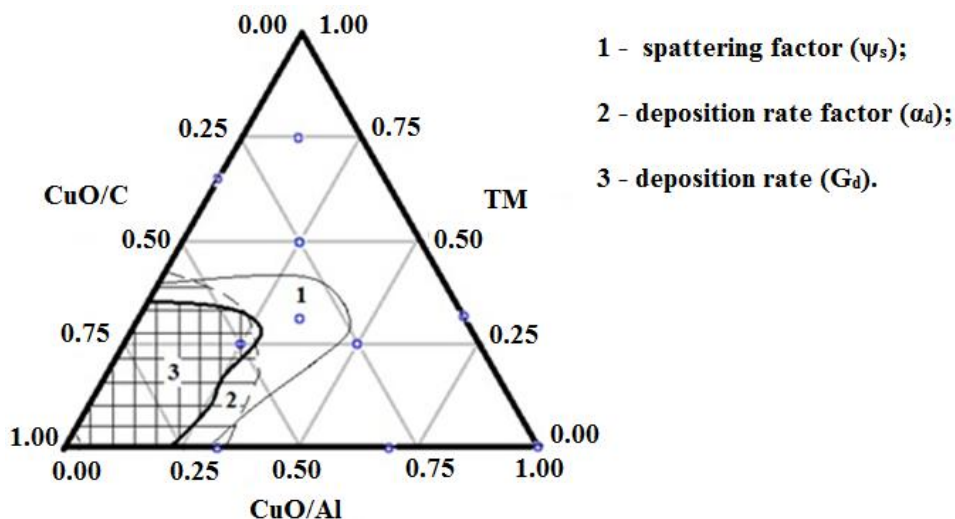


Fig. 3. Interpretation diagram of optimal value areas

It has been found that the optimum areas for the deposition rate (G_d), deposition rate factor (α_d) and spattering factor (ψ_s) are observed for the following values of the composition the core fillet of components: TM = 25...39, CuO/C = 5...6, CuO/Al = 3...4.

Conclusion

As a result of the studies performed, the nature of the effect of the exothermic mixture and the ratios of the exothermic mixture (CuO) oxidant to the exothermic mixture reducing agent (Al), i.e. CuO/Al, and the exothermic oxidizer (CuO) oxidant to the oxidizing agent to carbon (C) have been determined.

Mathematical models have been obtained and response surfaces for the deposition rate (G_d) indices, deposition factor (α_d), and spattering factor (ψ_s) depending on the content of the components of the exothermic mixture and the carbon core of the flux wire have been built.

The greatest effect on the welding and process characteristics of FCAW-S has the ratio of components of CuO/Al exothermic mixture.

High values of deposition rate and the lowest values of the spattering factor are achieved with a larger amount of aluminum powder, ie with the ratio of oxidant to reducing agent greater than their stoichiometric value, i.e. $\text{CuO/Al} = 3...4$.

References

- [1] John J. Coronado, Holman F. Caicedo, and Adolfo L. Gómez., “The effects of welding processes on abrasive wear resistance for hardfacing deposits”, *Tribology International*, vol. 42, no. 5, pp. 745–749, October, 2009.
- [2] I. K. Pohodnja, A. M. Suptel', and V. N. Shlepakov, *Svarka poroshkovej provolokoj [Flux-cored wire arc welding]*. Kiev, Ukraine: Naukova dumka Publ., 1972. [in Russian].
- [3] S. V. Zharykov, A. H. Hryn, and L. V. Vasyleva, “Optymyzatsyia rezhymov naplavky samozashchytanoi poroshkovoivo provolokoi s ekzotermicheskoivo smesiu” [“Optimization of surfacing modes with self-shielded flux-cored wire with an exothermic mixture”]. *Visnyk Donbaskoi derzhavnoi mashynobudivnoi akademii [Herald of the Donbass State Engineering Academy]*, vol. 38. no. 2, pp. 116–120, 2016. [in Russian].
- [4] B. Trembach, A. Grin, S. Zharikov, and I. Trembach, “Investigation of powder wire with the CuO/Al exothermic mixture”, *Visnyk Ternopil's'koho natsional'noho tekhnichnoho universytetu [Scientific journal of the Ternopil National Technical University]*, vol. 92. no. 4, pp. 13–23, January, 2018.
- [5] A. A. Erohin, *Osnovy svarki plavlenniem [Fundamentals of fusion welding]*. Moscow, Russia: Mashinostroenie Publ., 1973. [in Russian].
- [6] Ju. A. Juzvenko, G. A. Kiriljuk, and S. Ju. Krivchikov, “Model plavlennija samozashhitnoj poroshkovoivo provoloki” [“Self-shielded flux cored wire melting model”], *Avtomaticheskaja svarka [Automatic Welding]*, vol. 1. pp. 26–29, 1983. [in Russian].
- [7] Ju. A. Juzvenko, and G. A. Kiriljuk, *Naplavka poroshkovoivo provolokoj [Flux-cored wire surfacing]*. Moscow, Russia: Mashinostroenie Publ., 1973. [in Russian].
- [8] V. V. Chigarev, D. A. Zarechensky, and A. G. Belik, “Peculiarities of melting of flux-cored strips with exothermic mixtures contained in their filler”, *The Paton Welding Journal*, no. 2, 46–48, 2007.
- [9] Y. D. Park, N. Kang, S. H. Malene, and D. L. Olson, “Effect of exothermic additions on heat generation and arc process efficiency in flux-cored arc welding”, *Metals and Materials International*, vol. 13, no. 6, pp. 501–509, 2007.
- [10] O. M. Ioffe, O. M. Kuznecov, and V. M. Piteckij, “Vlijanie titano-termitnoj smesi, vhodjashhej v jelektroodnoe pokrytie, na povyshenie proizvoditel'nosti svarki” [“Effect of titanium-thermite mixture included in the electrode coating on increasing welding productivity”], *Svarochnoe proizvodstvo*, vol. 3, pp. 26–28, 1980. [in Russian].